


ARMY RESEARCH LABORATORY



# Fabrication of a Composite Airfoil With a Large Scale Twist Capability

by William A. Spurgeon and Charles Beauchamp

ARL-TN-179

June 2001

Approved for public release; distribution is unlimited.

20010814 044

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# **Army Research Laboratory**

Aberdeen Proving Ground, MD 21005-5069

---

**ARL-TN-179**

**June 2001**

---

## **Fabrication of a Composite Airfoil With a Large Scale Twist Capability**

**William A. Spurgeon**

Weapons and Materials Research Directorate, ARL

**Charles Beauchamp**

Naval Underwater Warfare Center

---

Approved for public release; distribution is unlimited.

---

---

## **Abstract**

---

This technical note describes the fabrication of a composite airfoil shaped part that could twist easily about its long axis, but would not flex easily. This part was fabricated using a polyurethane resin matrix glass reinforced composite material that performed satisfactorily in wind tunnel tests. Possibilities for scale-up to very large parts are described.

---

## **Contents**

---

<b>List of Figures</b>	<b>v</b>
<b>1. Introduction</b>	<b>1</b>
<b>2. Materials Selection</b>	<b>1</b>
<b>3. Airfoil Fabrication Details</b>	<b>2</b>
<b>4. Scale-Up Possibilities</b>	<b>5</b>
<b>5. Conclusions</b>	<b>7</b>
<b>6. References</b>	<b>9</b>
<b>Distribution List</b>	<b>11</b>
<b>Report Documentation Page</b>	<b>23</b>

INTENTIONALLY LEFT BLANK.

---

## List of Figures

---

Figure 1. The helicopter rotor blade section used as a mandrel for the airfoil fabrication process. ....	2
Figure 2. The SCRIMP process. Successive layers of Teflon-coated glass release fabric (brown layer at left of picture), fiberglass fabric (white layer) to make the part, A8888 polyamide release fabric (light green fabric) and transfer medium (dark green fabric) were applied over the mandrel. ....	3
Figure 3. A SCRIMP panel ready for infusion. The fill line is at the left, and the vacuum line is at the right. A black transfer medium was used in this case. ....	4
Figure 4. The first airfoil fabricated. ....	5
Figure 5. The second airfoil fabricated. ....	6
Figure 6. Another view of the second airfoil fabricated. ....	6

**INTENTIONALLY LEFT BLANK.**

---

## **1. Introduction**

---

This technical note describes the fabrication of a composite airfoil shaped part that could twist easily about its long axis, but would not flex easily. This was one of the significant challenges of a Federated Laboratory project to demonstrate the potential utility of such an airfoil as a windmill blade. Once the blade reaches a certain speed, the power generation efficiency of the blade can be improved if the blade is twisted around its long axis. The twist was introduced by applying a current to a shape-memory alloy wire wrapped around the part. The airfoil shaped part was fabricated using a glass fabric reinforced polyurethane elastomer matrix composite at a minimal cost. The materials selection, composite airfoil fabrication, and possibilities for scale-up to very large parts are described in this note. The performance of the airfoil was satisfactory, and twists well in excess of the needed 7 degrees were possible. Details of its modeled and measured performance will be presented elsewhere.

---

## **2. Materials Selection**

---

The elastomer selected for this project was Adiprene L-100 polyurethane cured with CATUR 21. Both components were manufactured by and obtained from Uniroyal Chemical.\* In previous U.S. Army Research Laboratory (ARL) work [1], this polyether-based polyurethane exhibited a hardness of Shore-A 85, somewhat harder than an automobile tire (Shore-A 75) and softer than a typewriter roller (Shore-A 90). Nearly all of the toluene-diisocyanate it contains is chemically bound, which makes it relatively safe to handle. Its most attractive feature is a fairly long working life, limited mainly by hydrolysis of the resin by moisture in the air. It is best worked at a temperature of about 140 degrees F. At this temperature, its viscosity drops to a low of about 2200 centipoise, which is low enough for some resin transfer molding processes. It cures rapidly at temperatures above 212 degrees F. Its glass transition temperature is below the -60 degree F limit of the differential scanning calorimeter used for this test. The resin has been used on other ARL projects that required a semi-flexible composite. Its selection followed an extensive search for appropriate thermoset resins through vendor contacts, in-house tests, and technical discussions with other DOD personnel.

---

\* Uniroyal Chemical Co., Inc., World Headquarters, Middlebury, CT 06749.

The glass fabric used for the project was a 24 oz per square yard 5 × 5 S-2 glass woven roving. This fabric has been used extensively for ARL armor work for at least the past 15 years. The sizing is the standard epoxy compatible/polyester semicompatible type 463 sizing.\* Apparently, no commercially available sizing has been specifically developed for polyurethane resins [2]. This fabric typically contributes 25 mil per ply to the thickness of a composite. Samples of such composites cut along a weave direction (0 or 90 degrees) will twist relatively easily, but will not flex well. In comparison, samples cut at 45 degrees will flex easily, but will resist twisting.

---

### 3. Airfoil Fabrication Details

---

The first major requirement for fabricating the airfoil was a mandrel of an appropriate size and shape over which fabrics could be draped or glass filaments wound. An approximately 5-ft-long section of a rotor blade for the UH-58 "Huey" helicopter was available for experimentation at ARL. This blade section is about 13-in wide and has a maximum width of 1.5 in. Although this is not an ideal airfoil shape, it was determined to be a sufficiently good approximation to start this project. The rotor blade used in the fabrication process is shown in Figure 1.



Figure 1. The helicopter rotor blade section used as a mandrel for the airfoil fabrication process.

---

\* Advanced Glassfiber Yarns, Aiken, SC.

The airfoil blanks were fabricated using a vacuum-assisted resin transfer molding process known as SCRIMP (Seeman's Composite Resin Infusion Molding Process [3]). This process is illustrated in Figures 2 and 3. First, the tool (in this case the rotor blade) was coated with five coats of Frekote 700 mold release.\* Next, a layer of nonporous Teflon-coated glass release film (Richmond 200TFNP)<sup>†</sup> was then laid over the rotor blade and taped in place. Two plies of glass fabric, 34 in wide  $\times$  50 in long, were placed over the release fabric with the 90 degree direction along the long axis of the rotor. A ply of Richmond A8888 open weave polyamide release fabric<sup>†</sup> was laid over the glass. The edges of these fabrics were also taped to the mandrel. A layer of transfer medium, such as the 40–50% shade dark-green plastic awningscreen,<sup>†</sup> also shown in Figure 2, is then placed over the part. This transfer medium is cut about 8 in shorter than the 34 in length of the part. This forces the resin to flow down through the part and thus completely fill out the part before it reaches the vacuum line.



Figure 2. The SCRIMP process. Successive layers of Teflon-coated glass release fabric (brown layer at left of picture), fiberglass fabric (white layer) to make the part, A8888 polyamide release fabric (light green fabric) and transfer medium (dark green fabric) were applied over the mandrel.

---

\* The Dexter Corporation, Frekote Products, 1 Seabrook Dr., Seabrook, NH 03874.

<sup>†</sup> Northern Fiberglass Sales, Inc., PO Box 2010, Hampton, NH 03483-5098.

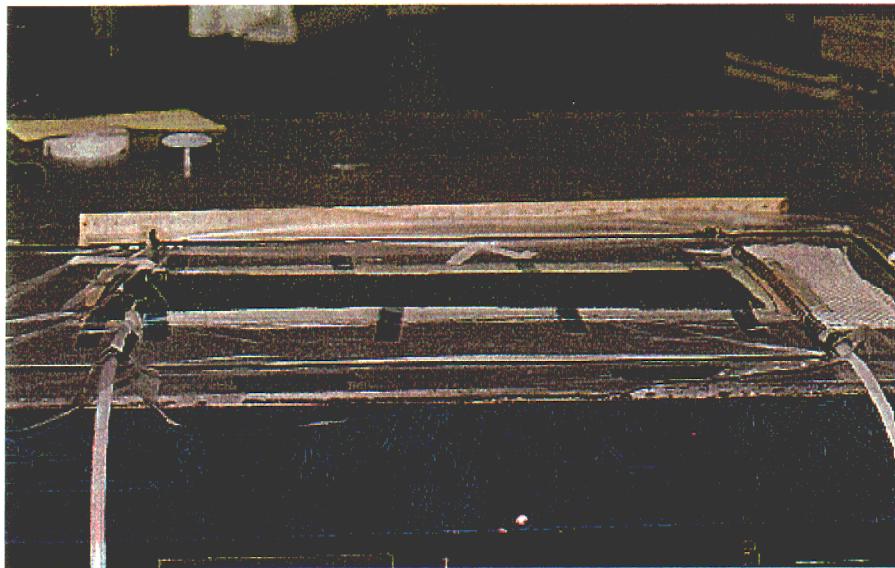


Figure 3. A SCRIMP panel ready for infusion. The fill line is at the left, and the vacuum line is at the right. A black transfer medium was used in this case.

The transfer medium is also cut about 1 in smaller than the part on the two perpendicular sides. This prevents the development of a low impedance path (a "race track") along the sides of the part. A vacuum line, made from stretched 0.5-in OD Panduit plastic electrical spiral wrapping (part number T62F)\* wrapped in a layer of 8.8-oz E or S-2 glass fabric, is placed at the end of the fabrics. A feed line in the form of a 0.75-in-diameter, 5-turn per inch steel spring was then placed on the leading edge of the rotor blade. Several layers of the transfer medium were used to separate it from the part. The entire assembly was then vacuum bagged (0.002-in-thick CAPRAN 512 bagging film† is the preferred material). Figure 3 shows a flat part vacuum bagged and ready for resin infusion. The fabrics were then infused with resin in a 140 degrees F walk-in oven. This process took about 1.5 hr. Once the resin transfer was complete, the blank was cured at 250 degrees F, debagged, and trimmed to size.

The airfoil blanks made in this manner had an open seam on the trailing edge of the parts. On the first part made, this was sealed at the 13-in width along a 1-in-wide flat. The Adiprene resin was used for the bonding since it results in a very strong bond—lap-shear samples prepared in this manner failed when the resin pulled off the glass [4]. The finished airfoil is shown in Figure 4.

---

\* Northern Fiberglass Sales, Inc., PO Box 2010, Hampton, NH.

† Graybar Electric Company, New Castle, DE.

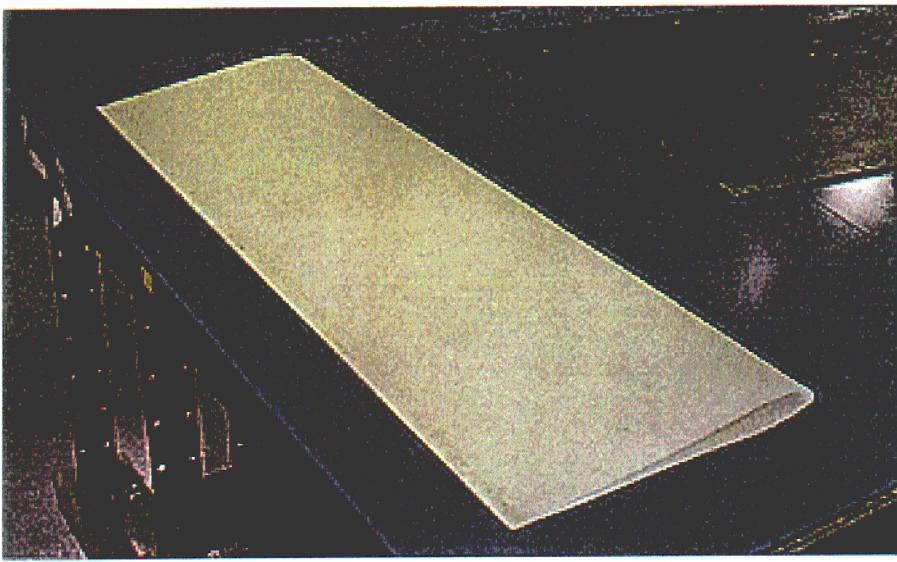


Figure 4. The first airfoil fabricated.

Ideal airfoils are somewhat fatter and symmetric. The second airfoil part was trimmed to a 9-in width; two 50-mil-thick, 1/4-in-wide strips of flat Adiprene-based composite stock were bonded in between the top and bottom of the airfoil part to make a somewhat more desirable airfoil. Two views of this airfoil are shown in Figures 5 and 6.

---

#### 4. Scale-Up Possibilities

---

The SCRIMP process employed in this effort was excellent for fabricating the narrow, thin airfoils that were made. It would be difficult to fabricate considerably larger and thicker airfoils by this process, since it is very slow with this viscous resin. However, a process known as FASTRAC (fast remotely activated channeling) [5, 6], newly developed at ARL, would be suitable for full-size windmill vanes. The ultimate thickness of parts that can be made by this process with the Adiprene resin has not been established, but may be as much as an inch. The vanes could be made thicker if necessary by repeated applications of the process. Since a temperature of 250 degrees F is all that is required to cure the resin, an oven of adequate size could easily be built around the part. The fabrics could be stitched at the trailing edge of the mandrel, eliminating the bonding step. Success in removing filament wound tubes made with the Adiprene resin indicates that the airfoils could be slid off the end of the mandrel without the aid of the open seam used in the current project.

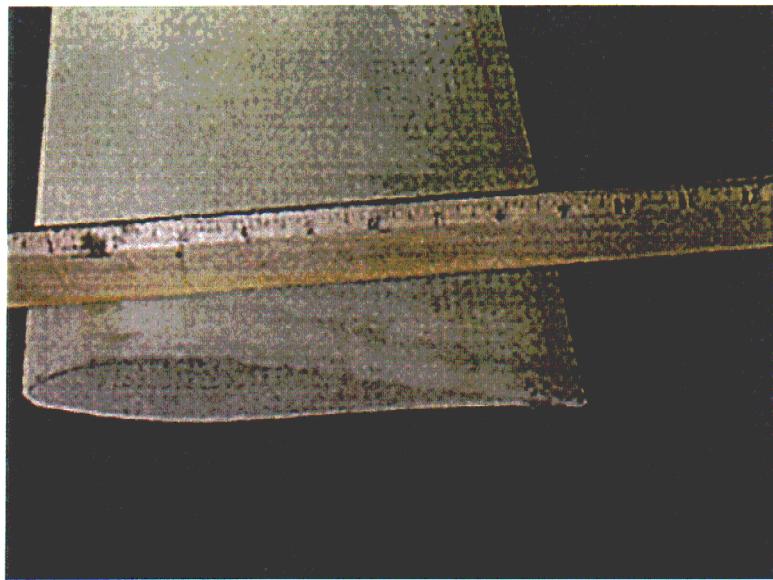


Figure 5. The second airfoil fabricated.

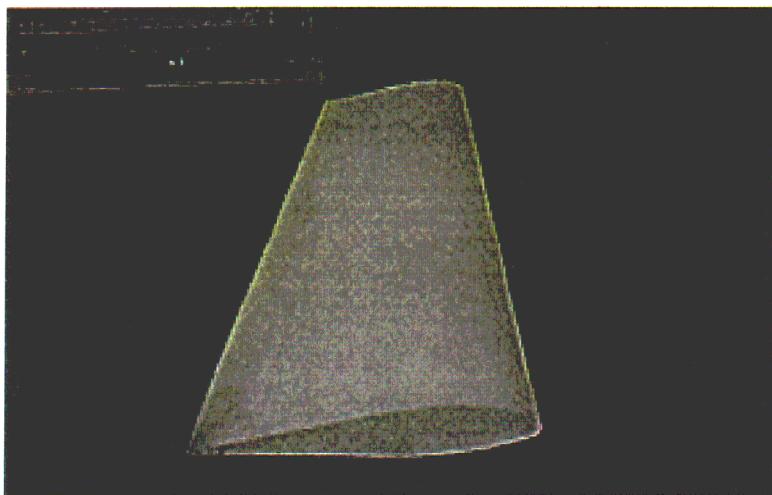


Figure 6. Another view of the second airfoil fabricated.

Depending on the size and shape of the airfoil, it may also be possible to braid the glass over the mandrel rather than using fabrics. This braided structure would then be infused with resin by a process such as FASTRAC. A stitched or stapled preform that could be similarly infused with resin may be a viable alternative to the braided structure. Filament winding would also be a possibility, provided that the part is not too large.

---

## **5. Conclusions**

---

The successful fabrication of a polyurethane composite airfoil for use as a windmill blade prototype was demonstrated on a 42-in-long part. Fabrication of a full size windmill blade would clearly require some developmental work, but there is ample reason to expect eventual success.

INTENTIONALLY LEFT BLANK.

---

## 6. References

---

1. Spurgeon, W. A., and D. J. Thomas. "Fabrication of Novel Bumper and Skirt Components for a Ground Vehicle." ARL-TR-2327, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, September 2000.
2. Collins, T. "Advanced Glassfiber Yarns." Personal communication, Aberdeen Proving Ground, MD, June 2000.
3. Seeman, W. H. "Plastic Transfer Molding Techniques for the Production of Fiber Reinforced Plastic Structures." U.S. Patent No. 4,902,215, 20 February 1990.
4. Spurgeon, W. A., and D. J. Thomas. "Fabrication of Novel Bumper and Skirt Components for a Ground Vehicle." ARL-TR-2327, Appendix A, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, September 2000.
5. Walsh, S. M., E. J. Rigas, W. A. Spurgeon, and D. J. Strand. *ICCE/7 Proceedings*, Denver, CO, pp. 903-904, July 2000.
6. Walsh, S. M., E. J. Rigas, W. A. Spurgeon, W. N. Roy, D. Heider, and J. Gillespie "A Non-Contact Distribution Scheme for Promoting and Controlling Resin Flow for VARTM Processes." SAMPE Technical Conference, Boston, MA, 5 November 2000.

**INTENTIONALLY LEFT BLANK.**

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218	1	DIRECTOR US ARMY RESEARCH LAB AMSRL CI AI R 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	HQDA DAMO FDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	OSD OUSD(A&T)/ODDR&E(R) DR R J TREW 3800 DEFENSE PENTAGON WASHINGTON DC 20301-3800	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI IS T 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	COMMANDING GENERAL US ARMY MATERIEL CMD AMCRDA TF 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001	<u>ABERDEEN PROVING GROUND</u>	
1	INST FOR ADVNCED TCHNLGY THE UNIV OF TEXAS AT AUSTIN 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316	2	DIR USARL AMSRL CI LP (BLDG 305)
1	DARPA SPECIAL PROJECTS OFFICE J CARLINI 3701 N FAIRFAX DR ARLINGTON VA 22203-1714		
1	US MILITARY ACADEMY MATH SCI CTR EXCELLENCE MADN MATH MAJ HUBER THAYER HALL WEST POINT NY 10996-1786		
1	DIRECTOR US ARMY RESEARCH LAB AMSRL D DR D SMITH 2800 POWDER MILL RD ADELPHI MD 20783-1197		

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DIRECTOR US ARMY RESEARCH LAB AMSRL CP CA D SNIDER 2800 POWDER MILL RD ADELPHI MD 20783-1145	1	DIRECTOR U S ARMY AMCOM SFAE AV RAM TV D CALDWELL BUILDING 5300 REDSTONE ARSENAL AL 35898
1	DIRECTOR US ARMY RESEARCH LAB AMSRL OP SD TA 2800 POWDER MILL ROAD ADELPHI MD 20783-1145	2	CDR USA AMCOM AVIATION APPLIED TECH DIR J SCHUCK FT EUSTIS VA 23604-5577
3	DIRECTOR US ARMY RESEARCH LAB AMSRL OP SD TL 2800 POWDER MILL ROAD ADELPHI MD 20783-1145	1	U S ARMY CRREL P DUTTA 72 LYME RD HANOVER NH 03755
2	DIRECTOR US ARMY RESEARCH LAB AMSRL OP CI AD TECH PUB BR RECORDS MGMT ADMIN 2800 POWDER MILL ROAD ADELPHI MD 20783-1197	1	US ARMY CERL R LAMPO 2902 NEWMARK DR CHAMPAIGN IL 61822
1	HQDA DAMI FIT NOLAN BUILDING WASHINGTON DC 20310-1025	2	U S ARMY CORP OF ENGINEERS CERC C T LIU CEW ET T TAN 20 MASS AVE NW WASHINGTON DC 20314
1	DIRECTOR PARTMENT OF THE ARMY OASARDA SARD-SO 3 ARMY PENTAGON WASHINGTON DC 20310-0103	1	US ARMY MATERIEL SYSTEMS ANALYSIS ACTIVITY P DIETZ 392 HOPKINS RD AMXSY TD APG MD 21005-5071
1	DEPUTY ASST SCY FOR R&T SARD TT RM 3EA79 THE PENTAGON WASHINGTON DC 20301-7100	1	DIRECTOR US ARMY RESEARCH LAB AMSRL OP APL APG MD 21005-5066
1	COMMANDER US ARMY MATERIEL COMMAND AMXMI INT 5001 EISENHOWER AVENUE ALEXANDRIA VA 22333-0001		

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
8	COMMANDER US ARMY TACOM ASMTA TR R D THOMAS J BENNETT D HANSEN AMSTA JSK S GOODMAN J FLORENCE AMSTA-TR-D D OSTBERG L HINOJOSA B RAJU WARREN MI 48397-5000	3	NAVAL UNDERWATER WARFARE CTR CODE 8232 BLDG 1302 02 J GOMEZ C BEAUCHAMP S PLUNKETT 1176 HOWELL ST NEWPORT RI 02841
3	DIRECTOR US ARMY NATIONAL GROUND INTELLIGENCE CTR D LEITER S CARTER S MINGLEDORF 220 SEVENTH STREET NE CHARLOTTESVILLE VA 22091	1	DIRECT REPORTING PROGRAM MANAGER ADVANCED AMPHIBIOUS ASSAULT VEHICLE 991 ANNAPOLIS WAY WOODBRIDGE VA 22191-1215
1	US ARMY SBCCOM SOLDIER SYSTEMS CENTER BUS AREA ADVOCACY TEAM W HASKELL KANSAS ST NATICK MA 01760-5019	1	NAVAL SURFACE WARFARE CTR DAHLGREN DIV CODE G06 DAHLGREN VA 22448
8	US ARMY RESEARCH OFC A CROWSON J CHANDRA J PRATER R SINGLETON G ANDERSON D STEPP D KISEROW J CHANG PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709-2211	1	NAVAL SURFACE WARFARE CTR TECH LIBRARY CODE 323 17320 DAHLGREN RD DAHLGREN VA 22448
3	NAVAL RESEARCH LAB I WOLOCK CODE 6383 R BADALIANCE CODE 6304 L GAUSE WASHINGTON DC 20375	3	NAVAL RESEARCH LAB I WOLOCK CODE 6383 R BADALIANCE CODE 6304 L GAUSE WASHINGTON DC 20375
1	NAVAL SURFACE WARFARE CTR CRANE DIVISION M JOHNSON CODE 20H4 LOUISVILLE KY 40214-5245	1	NAVAL SURFACE WARFARE CTR CRANE DIVISION M JOHNSON CODE 20H4 LOUISVILLE KY 40214-5245
2	COMMANDER NAVAL SURFACE WARFARE CTR CARDEROCK DIVISION R PETERSON CODE 2020 M CRITCHFIELD CODE 1730 BETHESDA MD 20084	2	COMMANDER NAVAL SURFACE WARFARE CTR CARDEROCK DIVISION R PETERSON CODE 2020 M CRITCHFIELD CODE 1730 BETHESDA MD 20084
1	NAVAL AIR SYSTEMS COMMAND J THOMPSON 48142 SHAW RD UNIT 5 PATUXENT RIVER MD 20670	2	NAVAL SURFACE WARFARE CTR U SORATHIA C WILLIAMS CD 6551 9500 MACARTHUR BLVD WEST BETHESDA MD 20817

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DAVID TAYLOR RESEARCH CTR SHIP STRUCTURES & PROTECTION DEPARTMENT/CODE 1702 BETHESDA MD 20084	1	NAVSEA OJRI PEO DD21 PMS500 G CAMPONESCHI 2351 JEFFERSON DAVIS HWY ARLINGTON VA 22242-5165
2	DAVID TAYLOR RESEARCH CTR R ROCKWELL W PHYLLAIER BETHESDA MD 20054-5000	1	AFRL MLBC 2941 P ST RM 136 WRIGHT PATTERSON AFB OH 45433-7750
1	OFC OF NAVAL RESEARCH D SIEGEL CODE 351 800 N QUINCY ST ARLINGTON VA 22217-5660	1	AFRL MLSS R THOMSON 2179 12TH ST RM 122 WRIGHT PATTERSON AFB OH 45433-7718
8	NAVAL SURFACE WARFARE CTR J FRANCIS CODE G30 D WILSON CODE G32 R D COOPER CODE G32 J FRAYSSE CODE G33 E ROWE CODE G33 T DURAN CODE G33 L DE SIMONE CODE G33 R HUBBARD CODE G33 DAHLGREN VA 22448	2	AFRL F ABRAMS J BROWN BLDG 653 2977 P ST STE 6 WRIGHT PATTERSON AFB OH 45433-7739
1	NAVAL SEA SYSTEMS CMD D LIESE 2531 JEFFERSON DAVIS HWY ARLINGTON VA 22242-5160	1	AFRL MLS OL L COULTER 7278 4TH ST BLDG 100 BAY D HILL AFB UT 84056-5205
1	NAVAL SURFACE WARFARE CTR M LACY CODE B02 17320 DAHLGREN RD DAHLGREN VA 22448	1	DEFENSE NUCLEAR AGENCY INNOVATIVE CONCEPTS DIV 6801 TELEGRAPH RD ALEXANDRIA VA 22310-3398
2	OFC OF NAVAL RESEARCH D SIEGEL CODE 351 J KELLY 800 N QUINCY ST ARLINGTON VA 22217-56601	1	WATERWAYS EXPERIMENT D SCOTT 3909 HALLS FERRY RD SC C VICKSBURG MS 39180
2	NAVAL SURFACE WARFARE CTR CARDEROCK DIVISION R CRANE CODE 2802 C WILLIAMS CODE 6553 3A LEGGETT CIR BETHESDA MD 20054-5000	3	DARPA M VANFOSSEN S WAX L CHRISTODOULOU 3701 N FAIRFAX DR ARLINGTON VA 22203-1714

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	SERDP PROGRAM OFC PM P2 C PELLERIN B SMITH 901 N STUART ST STE 303 ARLINGTON VA 22203	7	NIST R PARNAS J DUNKERS M VANLANDINGHAM MS 8621 J CHIN MS 8621 D HUNSTON MS 8543 J MARTIN MS 8621 D DUTHINH MS 8611 100 BUREAU DR GAITHERSBURG MD 20899
1	FAA MIL HDBK 17 CHAIR L ILCEWICZ 1601 LIND AVE SW ANM 115N RESTON VA 98055	1	OAK RIDGE NATIONAL LABORATORY C EBERLE MS 8048 PO BOX 2008 OAK RIDGE TN 37831
2	FAA TECH CENTER D OPLINGER AAR-431 P SHYPRYKEVICH AAR 431 ATLANTIC CITY NJ 08405	1	OAK RIDGE NATIONAL LABORATORY C D WARREN MS 8039 PO BOX 2008 OAK RIDGE TN 37831
1	US DEPT OF ENERGY OFC OF ENVIRONMENTAL MANAGEMENT P RITZCOVAN 19901 GERMANTOWN RD GERMANTOWN MD 20874-1928	1	HYDROGEOLOGIC INC SERDP ESTCP SPT OFC S WALSH 1155 HERNDON PKWY STE 900 HERNDON VA 201701
5	DIRECTOR LLNL R CHRISTENSEN S DETERESA F MAGNESS M FINGER MS 313 M MURPHY L 282 PO BOX 808 LIVERMORE CA 94550	3	DIRECTOR SANDIA NATIONAL LABS APPLIED MECHANICS DEPT DIVISION 8241 W KAWAHARA K PERANO D DAWSON P NIELAN PO BOX 969 LIVERMORE CA 94550-0969
1	DIRECTOR LLNL F ADDESSIO MS B216 PO BOX 1633 LOS ALAMOS NM 87545	3	NASA Langley RSCH CTR AMSRL VS W ELBER MS 266 F BARTLETT JR MS 266 G FARLEY MS 266 HAMPTON VA 23681-0001
1	OAK RIDGE NATIONAL LABORATORY R M DAVIS PO BOX 2008 OAK RIDGE TN 37831-6195	1	NASA Langley RSCH CTR T GATES MS 188E HAMPTON VA 23661-3400

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	USDOT FEDERAL RAILRD M FATEH RDV 31 WASHINGTON DC 20590	1	COMPOSITE MATERIALS INC R HOLLAND 11 JEWEL CT ORINDA CA 945631
1	DOT FHWA J SCALZI 400 SEVENTH ST SW 3203 HNG 32 WASHINGTON DC 20590	1	COMPOSITE MATERIALS INC C RILEY 14530 S ANSON AVE SANTA FE SPRINGS CA 90670
1	FHWA E MUNLEY 6300 GEORGETOWN PIKE MCLEAN VA 22101	2	COMPOSIX D BLAKE L DIXON 120 O NEILL DR HEBRUN OH 43025
1	CENTRAL INTLLGNC AGNCY OTI WDAG GT W L WALTMAN PO BOX 1925 WASHINGTON DC 20505	4	CYTEC FIBERITE R DUNNE D KOHLI M GILLIO R MAYHEW
1	DIRECTOR NATIONAL GRND INTLLGNC CTR IANG TMT 220 SEVENTH ST NE CHARLOTTESVILLE VA 22902-5396		1300 REVOLUTION ST HAVRE DE GRACE MD 21078
1	DIRECTOR DEFENSE INTLLGNC AGNCY TA 5 K CRELLING WASHINGTON DC 20310	2	SIMULA J COLTMAN R HUYETT 10016 S 51ST ST PHOENIX AZ 85044
1	GRAPHITE MASTERS INC J WILLIS 3815 MEDFORD ST LOS ANGELES CA 90063-1900	1	SIOUX MFG B KRIEL PO BOX 400 FT TOTTEN ND 58335
1	ADVANCED GLASS FIBER YARNS T COLLINS 281 SPRING RUN LANE STE A DOWNINGTON PA 19335	2	PROTECTION MATERIALS INC M MILLER F CRILLEY 14000 NW 58 CT MIAMI LAKES FL 33014
1	COMPOSITE MATERIALS INC D SHORTT 19105 63 AVE NE PO BOX 25 ARLINGTON WA 98223	3	FOSTER MILLER JJ GASSNER M ROYLANCE W ZUKAS 195 BEAR HILL RD WALTHAM MA 02354-1196
		1	ROM DEVELOPMENT CORP R O MEARA 136 SWINEBURNE ROW BRICK MARKET PLACE NEWPORT RI 02840

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	JPS GLASS L CARTER PO BOX 260 SLATER RD SLATER SC 29683	2	GLCC INC J RAY M BRADLEY 103 TRADE ZONE DR STE 26C WEST COLUMBIA SC 29170
1	O GARA HESS & EISENHARDT M GILLESPIE 9113 LESAINT DR FAIRFIELD OH 45014	1	SAIC G CHRYSSOMALLIS 3800 W 80TH ST STE 1090 BLOOMINGTON MN 5543111
1	CONNEAUGHT INDUSTRIES INC J SANTOS PO BOX 1425 COVENTRY RI 02816	1	AAI CORPORATION T G STASTNY PO BOX 126 HUNT VALLEY MD 21030-0126
1	BATTELLE C R HARGREAVES 505 KING AVE COLUMBUS OH 43201-2681	1	APPLIED COMPOSITES W GRISCH 333 NORTH SIXTH ST ST CHARLES IL 60174
1	BATTELLE NATICK OPNS B HALPIN 209 W CENTRAL ST STE 302 NATICK MA 01760	3	HEXCEL INC R BOE F POLICELLI J POESCH PO BOX 98 MAGNA UT 84044
1	BATTELLE NW DOE PNNL T HALL MS K231 BATTELLE BLVD RICHLAND WA 99352	1	ZERNOW TECHNICAL SERVICES L ZERNOW 425 W BONITA AVE STE 208 SAN DIMAS CA 91773
3	PACIFIC NORTHWEST LAB M SMITH G VAN ARSDALE R SHIPPELL PO BOX 999 RICHLAND WA 99352	2	OLIN CORPORATION FLINCHBAUGH DIV E STEINER B STEWART PO BOX 127 RED LION PA 17356
1	ARMTEC DEFENSE PRODUCTS S DYER 85 901 AVE 53 PO BOX 848 COACHELLA CA 92236	1	OLIN CORPORATION L WHITMORE 10101 NINTH ST NORTH ST PETERSBURG FL 33702
2	ADVANCED COMPOSITE MATS CORP P HOOD J RHODES 1525 S BUNCOMBE RD GREER SC 29651-9208	1	GKN AEROSPACE D OLDS 15 STERLING DR WALLINGFORD CT 06492

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
5	SIKORSKY AIRCRAFT G JACARUSO T CARSTENSAN B KAY S GARBO MS S330A J ADELMANN 6900 MAIN ST PO BOX 9729 STRATFORD CT 06497-9729	1	BOEING DOUGLAS PRODUCTS DIV L J HART SMITH 3855 LAKEWOOD BLVD D800 0019 LONG BEACH CA 90846-0001
1	PRATT & WHITNEY D HAMBRICK 400 MAIN ST MS 114 37 EAST HARTFORD CT 06108	1	LOCKHEED MARTIN S REEVE 8650 COBB DR D 73 62 MZ 0648 MARIETTA GA 30063-0648
1	AEROSPACE CORP G HAWKINS M4 945 2350 E EL SEGUNDO BLVD EL SEGUNDO CA 90245	1	LOCKHEED MARTIN SKUNK WORKS D FORTNEY 1011 LOCKHEED WAY PALMDALE CA 93599-2502
2	CYTEC FIBERITE M LIN W WEB 1440 N KRAEMER BLVD ANAHEIM CA 92806	1	LOCKHEED MARTIN R FIELDS 1195 IRWIN CT WINTER SPRINGS FL 32708
1	HEXCEL T BITZER 11711 DUBLIN BLVD DUBLIN CA 94568	1	MATERIALS SCIENCES CORP B W ROSEN 500 OFC CENTER DR STE 250 FT WASHINGTON PA 19034
1	BOEING R BOHLMANN PO BOX 516 MC 5021322 ST LOUIS MO 63166-0516	2	NORTHROP GRUMMAN ENVIRONMENTAL PROGRAMS R OSTERMAN A YEN 8900 E WASHINGTON BLVD PICO RIVERA CA 90660
2	BOEING DFNSE & SPACE GP W HAMMOND S 4X55 J RUSSELL S 4X55 PO BOX 3707 SEATTLE WA 98124-2207	1	UDLP D MARTIN PO BOX 359 SANTA CLARA CA 95052
2	BOEING ROTORCRAFT P MINGURT P HANDEL 800 B PUTNAM BLVD WALLINGFORD PA 19086	2	UDLP G THOMAS T PIKE PO BOX 58123 SANTA CLARA CA 95052
		2	UDLP R BARRETT MAIL DROP M53 V HORVATICH MAIL DROP M53 328 W BROKAW RD SANTA CLARA CA 95052-0359

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
3	UDLP R BRYNSVOLD 4800 EAST RIVER RD MINNEAPOLIS MN 55421-1498	2	CIVIL ENGR RSCH FOUNDATION PRESIDENT H BERNSTEIN R BELLE 1015 15TH ST NW STE 600 WASHINGTON DC 20005
3	UDLP GROUND SYSTEMS DIVISION M PEDRAZZI MAIL DROP N09 A LEE MAIL DROP N11 M MACLEAN MAIL DROP N06 1205 COLEMAN AVE SANTA CLARA CA 95052	1	ARROW TECH ASSO 1233 SHELBOURNE RD STE D8 SOUTH BURLINGTON VT 05403-7700
2	GENERAL DYNAMICS AMPHIBIOUS SYS SURVIVABILITY LEAD G WALKER D LEAP 991 ANNAPOLIS WAY WOODBRIDGE VA 22191	1	R EICHELBERGER CONSULTANT 409 W CATHERINE ST BEL AIR MD 21014-3613
2	GDLS D REES M PASIK PO BOX 2074 WARREN MI 48090-2074	1	UCLA MANE DEPT ENGR IV H T HAHN LOS ANGELES CA 90024-1597
1	GDLS DIVISION D BARTLE PO BOX 1901 WARREN MI 48090	2	UNIV OF DAYTON RESEARCH INST R Y KIM A K ROY 300 COLLEGE PARK AVE DAYTON OH 45469-0168
1	GDLS MUSKEGON OPERATIONS W SOMMERS JR 76 GETTY ST MUSKEGON MI 49442	1	MIT P LAGACE 77 MASS AVE CAMBRIDGE MA 01887
6	INST FOR ADVANCED TECH H FAIR I MCNAB P SULLIVAN S BLESS W REINECKE C PERSAD 3955 W BRAKER LN STE 400 AUSTIN TX 78759-5316	1	IIT RESEARCH CENTER D ROSE 201 MILL ST ROME NY 13440-6916
		1	MICHIGAN ST UNIV MSM DEPT R AVERILL 3515 EB EAST LANSING MI 48824-1226
		1	UNIV OF KENTUCKY L PENN 763 ANDERSON HALL LEXINGTON KY 40506-0046

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	UNIV OF WYOMING D ADAMS PO BOX 3295 LARAMIE WY 82071	1	DEPT OF MATERIALS SCIENCE & ENGINEERING UNIVERSITY OF ILLINOIS AT URBANA CHAMPAIGN J ECONOMY 1304 WEST GREEN ST 115B URBANA IL 61801
1	UNIVERSITY OF UTAH DEPT OF MECH & INDUSTRIAL ENGR S SWANSON SALT LAKE CITY UT 84112	3	UNIV OF TEXAS AT AUSTIN CTR FOR ELECTROMECHANICS J PRICE A WALLS J KITZMILLER 10100 BURNET RD AUSTIN TX 78758-4497
2	PENN STATE UNIV R MCNITT C BAKIS 212 EARTH ENGR SCIENCES BLDG UNIVERSITY PARK PA 16802	3	VA POLYTECHNICAL INST & STATE UNIV DEPT OF ESM M W HYER K REIFSNIDER R JONES BLACKSBURG VA 24061-0219
1	PENN STATE UNIV R S ENGEL 245 HAMMOND BLDG UNIVERSITY PARK PA 16801	1	NORTH CAROLINA STATE UNIV CIVIL ENGINEERING DEPT W RASDORF PO BOX 7908 RALEIGH NC 27696-7908
1	PURDUE UNIV SCHOOL OF AERO & ASTRO C T SUN W LAFAYETTE IN 47907-1282	1	UNIV OF MARYLAND DEPT OF AEROSPACE ENGNRNG A J VIZZINI COLLEGE PARK MD 207421
1	STANFORD UNIV DEPT OF AERONAUTICS & AEROBALLISTICS S TSAI DURANT BLDG STANFORD CA 94305	1	DREXEL UNIV A S D WANG 32ND & CHESTNUT ST PHILADELPHIA PA 19104
1	UNIV OF DAYTON J M WHITNEY COLLEGE PARK AVE DAYTON OH 45469-0240	1	SOUTHWEST RSCH INST ENGR & MATL SCIENCES DIV J RIEGEL 6220 CULEBRA RD PO DRAWER 28510 SAN ANTONIO TX 78228-0510
2	UNIV OF DELAWARE CTR FOR COMPOSITE MTRLS J GILLESPIE D HEIDER 201 SPENCER LABORATORY NEWARK DE 19716		

NO. OF  
COPIES ORGANIZATION

NO. OF  
COPIES ORGANIZATION

ABERDEEN PROVING GROUND

64 DIR USARL  
AMSRL CS IO FI  
M ADAMSON  
AMSRL WM B  
A HORST  
AMSRL WM BR  
C SHOEMAKER  
J BORNSTEIN  
AMSRL WM M  
D VIECHNICKI  
G HAGNAUER  
J MCCUALEY  
AMSRL WM MA  
D FLANAGAN  
D HARRIS  
S MCKNIGHT  
P MOY  
P PATTERSON  
G RODRIGUEZ  
A TEETS  
R YIN  
AMSRL WM MB  
B FINK  
J BENDER  
T BLANAS  
T BOGETTI  
R BOSSOLI  
L BURTON  
S CORNELISON  
P DEHMER  
W DRYSDALE  
S GHIORSE  
D GRANVILLE  
C HOPPEL  
D HENRY  
R KASTE  
M KLUSEWITZ  
M LEADORE  
R LIEB  
E RIGAS  
J SANDS  
D SPAGNUOLO  
W SPURGEON  
J TZENG  
E WETZEL

ABERDEEN PROVING GROUND (CONT)

AMSRL WM MB ALC  
A ABRAHAMIAN  
M BERMAN  
A FRYDMAN  
T LI  
W MCINTOSH  
E SZYMANSKI  
AMRSL WM MC  
J BEATTY  
J SWAB  
J WELLS  
AMSRL WM MD  
W ROY  
S WALSH  
D STRAND  
AMSRL WM T  
B BURNS  
AMSRL WM TD  
T HADUCH  
T MOYNIHAN  
F GREGORY  
AMSRL WM TE  
A NIILER  
AMSRL SS SD  
H WALLACE

**INTENTIONALLY LEFT BLANK.**

# REPORT DOCUMENTATION PAGE

*Form Approved  
OMB No. 0704-0188*

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project(0704-0188), Washington, DC 20503.

<b>1. AGENCY USE ONLY (Leave blank)</b>			<b>2. REPORT DATE</b> June 2001	<b>3. REPORT TYPE AND DATES COVERED</b> Final, April 2000–October 2000
<b>4. TITLE AND SUBTITLE</b> Fabrication of a Composite Airfoil With a Large Scale Twist Capability			<b>5. FUNDING NUMBERS</b> 622618H80	
<b>6. AUTHOR(S)</b> William Spurgeon and Charles Beauchamp*				
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> U.S. Army Research Laboratory ATTN: AMSRL-WM-MB Aberdeen Proving Ground, MD 21005-5069			<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> ARL-TN-179	
<b>9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)</b> Naval Underwater Warfare Center, 1176 Howell Street, Newport, RI 02841			<b>10. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>11. SUPPLEMENTARY NOTES</b> *Naval Underwater Warfare Center, 1176 Howell Street, Newport, RI 02841				
<b>12a. DISTRIBUTION/AVAILABILITY STATEMENT</b> Approved for public release; distribution is unlimited.			<b>12b. DISTRIBUTION CODE</b>	
<b>13. ABSTRACT</b> (Maximum 200 words)  This technical note describes the fabrication of a composite airfoil shaped part that could twist easily about its long axis, but would not flex easily. This part was fabricated using a polyurethane resin matrix glass reinforced composite material that performed satisfactorily in wind tunnel tests. Possibilities for scale-up to very large parts are described.				
<b>14. SUBJECT TERMS</b> flexible composite, polyurethane, airfoil			<b>15. NUMBER OF PAGES</b> 24	
			<b>16. PRICE CODE</b>	
<b>17. SECURITY CLASSIFICATION OF REPORT</b> UNCLASSIFIED	<b>18. SECURITY CLASSIFICATION OF THIS PAGE</b> UNCLASSIFIED	<b>19. SECURITY CLASSIFICATION OF ABSTRACT</b> UNCLASSIFIED	<b>20. LIMITATION OF ABSTRACT</b> UL	

**INTENTIONALLY LEFT BLANK.**

## USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-TN-179 (Spurgeon) Date of Report June 2001

2. Date Report Received \_\_\_\_\_

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_

Organization \_\_\_\_\_

CURRENT  
ADDRESS

Name \_\_\_\_\_ E-mail Name \_\_\_\_\_

Street or P.O. Box No. \_\_\_\_\_

City, State, Zip Code \_\_\_\_\_

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

Organization \_\_\_\_\_

OLD  
ADDRESS

Name \_\_\_\_\_

Street or P.O. Box No. \_\_\_\_\_

City, State, Zip Code \_\_\_\_\_

(Remove this sheet, fold as indicated, tape closed, and mail.)  
**(DO NOT STAPLE)**

---

DEPARTMENT OF THE ARMY


OFFICIAL BUSINESS

**BUSINESS REPLY MAIL**  
FIRST CLASS PERMIT NO 0001,APG,MD

POSTAGE WILL BE PAID BY ADDRESSEE

DIRECTOR  
US ARMY RESEARCH LABORATORY  
ATTN AMSRL WM MB  
ABERDEEN PROVING GROUND MD 21005-5069

---



NO POSTAGE  
NECESSARY  
IF MAILED  
IN THE  
UNITED STATES

A set of ten thick horizontal black lines, typically used for business reply mail, indicating where postage should be paid.